

Circular dichroism in planar nonchiral plasmonic metamaterials

Vassilios Yannopapas¹

¹*Department of Materials Science, School of Natural Sciences,
University of Patras, GR-26504 Patras, Greece*

It is shown theoretically that a nonchiral, two-dimensional array of metallic spheres exhibits optical activity as manifested in calculations of circular dichroism. The metallic spheres occupy the sites of a rectangular lattice and for off-normal incidence they show a strong circular-dichroism effect around the surface plasmon frequencies. The optical activity is a result of the rectangular symmetry of the lattice which gives rise to different polarizations modes of the crystal along the two orthogonal primitive lattice vectors. These two polarization modes result in a net polar vector, which forms a chiral triad with the wavevector and the vector normal to the plane of spheres. The formation of this chiral triad is responsible for the observed circular dichroism, although the structure itself is intrinsically nonchiral.

© 2009 Optical Society of America

OCIS codes: 160.3918, 160.1585, 240.6680, 310.6628

Author's email address is: vyannop@upatras.gr

Metamaterials is new class of artificial materials possessing properties and capabilities which are not met in their constituent (naturally occurring) materials. The majority of the recent work in this field focuses on the achievement of subwavelength structures with negative refractive index (NRI). This can be achieved when the effective per-

mittivity and permeability of the metamaterial become simultaneously negative in a common spectral region [1, 2]. In an alternative route, a NRI can occur in a chiral material consisting of resonant elements [3]. There have been several theoretical proposals [4, 5, 6, 7, 8, 9, 10, 11, 12, 13, 14] of artificial chiral metamaterials exhibiting NRI but only recently there has been experimental confirmation of chirality-assisted NRI [15, 16]. In

this work, the optical activity and the resulting NRI stem either from the helical symmetry of the elements repeated periodically in the metamaterial or from the helical symmetry of the underlying three-dimensional (3D) lattice. Recently, strong optical activity has been reported in a two-dimensional (2D) nonchiral metamaterial [17, 18]. The latter was realized as a perforated thin metallic sheet consisting of a square array of pairs of arcs of different length. This structure exhibited strong circular dichroism for off normal incidence of circular plane waves and in the case where the plane of incidence did not contain the polar vector of the unit cell. The polar vector occurred from the asymmetry of the unit cell (arcs of unequal length); this vector along with the wavevector and the normal to the metamaterial sheet form a chiral triad resulting in the observed optical activity. The above effect has been termed as extrinsic chirality [17] due to the nonchiral nature of the studied structures.

In the present Letter we employ a relatively simpler nonchiral 2D metamaterial exhibiting strong circular dichroism. The metamaterial consists of metallic (plasma) spheres occupying the sites of rectangular lattice. A rectangular lattice is, by definition, a 2D anisotropic system which possesses two principal polarization directions. Under plane wave illumination and around the dipolar

surface plasmon resonance, the above structure exhibits two distinct absorption peaks corresponding to the two different polarization modes resulting from the anisotropy of the lattice. For oblique incidence and circular polarization, the absorbance of the metamaterial depends on the state of polarization (left or right polarization) as long as the two principal axes of the metamaterial are not contained in the plane of incidence. The metamaterial under study operates in the optical regime where the optical activity is manifested within the surface-plasmon band of the metallic spheres. As such, it constitutes a much more realistic proposal of a planar, optically active metamaterial in the visible regime than the miniaturization of the corresponding ones of Refs. 18 and 17. Furthermore, the inclusion of plasmonic materials (metals) in artificial chiral structures greatly enhances gyrotropic effects when compared with naturally occurring chiral materials [19, 20, 21].

Fig. 1 shows the plasmonic metamaterial under study: a lattice with a rectangular unit cell with sides a and b , occupied by metallic spheres described by a Drude-type dielectric function, i.e., $\epsilon(\omega) = 1 - \omega_p^2 / [\omega(\omega + i\gamma)]$, where ω_p is the plasma frequency of the metal and γ is the loss factor which is taken to be $\gamma = 0.01\omega_p$, a typical value for metallic nanoparticles. The radius of the plasma spheres is

taken to be $S = 0.3c/\omega_p$. The optical properties of the above structure have been studied by means of the layer-multiple-scattering (LMS) method which is based on an ab initio multiple-scattering theory, using a well documented computer code [22, 23]. The LMS method is ideally suited for the calculation of the transmission, reflection and absorption coefficients of an electromagnetic (EM) wave incident on a composite slab consisting of a number of layers which can be either planes of non-overlapping particles with the same 2D periodicity or homogeneous plates. For each plane of particles, the method calculates the full multipole expansion of the total multiply scattered wave field and deduces the corresponding transmission and reflection matrices in the plane-wave basis. The transmission and reflection matrices of the composite slab are evaluated from those of the constituent layers.

In what follows we study the absorption spectra for right- and left-circularly polarized plane waves, denoted by A_R and A_L . The corresponding dichroism is given by the difference of the above absorption spectra, i.e., $\Delta = A_R - A_L$. We have considered the general case of oblique incidence where the incident wavevector is defined by the angles θ and ϕ shown in Fig. 1. Fig. 2a shows the absorbance for left- and right-circularly polarized (RCP-solid curve and LCP-broken

curve, respectively) incident light with $\theta = \phi = 45^\circ$. Both RCP and LCP curves exhibit two main absorption bands corresponding to the two different dipolar EM modes stemming from the coupling of neighboring spheres along the two principal axes of the lattice. We note that under circularly polarized plane-wave illumination, both modes are excited. In the case of normally incident wave polarized along one of the principal axis, only one of the modes is excited and a single, dipolar peak is observed [24]. The high-frequency absorption band possesses an inner structure which stems from the excitation of higher-multipole surface plasmons [24]. The main finding of Fig. 2a is the fact that the light absorption strongly depends on the state of circular polarization of the incident wave; this is also manifested in the dichroism curve of Fig. 2b. We note that the dichroism vanishes for normal incidence as well as for oblique incidence where $\phi = 0^\circ$ or 90° in which case the parallel (to the surface) component of the wavevector coincides with one of the two principal directions of the rectangular lattice. This is due to the fact that, in order to achieve circular dichroism in our case, the direction of the incident light must constitute a “screw direction” of the unit cell, i.e. the wavevector, the vector normal to the surface and one of the two primitive lattice vectors must form a chiral triad [17, 18, 25].

In Fig. 3 we show circular dichroism spectra for a fixed angle $\theta = 45^\circ$ and for different values of ϕ . As expected, the dichroism spectra have opposite signs for opposite values of ϕ which correspond to two enantiomeric arrangements. In general, the spectral bands of circular dichroism for the different values of ϕ have more or less the same width and height. Fig. 4 depicts optical activity spectra for fixed $\theta = \phi = 45^\circ$ and for different values of the side b of the rectangular unit cell. Since the optical activity is lost for a square array of spheres, as b/a increases from unity, we expect the circular dichroism to increase. This is evident by comparing the curves for $b = 1.25a$ and $b = 1.5a$. However, for larger values of b , the trend is reversed and the optical activity is suppressed. This is due to the fact that as b increases, the lattice becomes very dilute, the coupling of neighboring spheres in the y -direction diminishes and so does the light absorption (for both modes of circular polarization).

In conclusion, it has been shown that a nonchiral planar lattice of metallic spheres exhibits strong optical activity around the surface plasmon frequencies, under suitable conditions of light incidence. The structure can be fabricated by contemporary fabrication techniques [26] and used as a compact optically-active component in nanostructured devices.

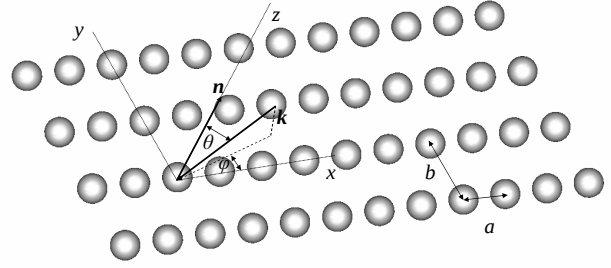


Fig. 1. Rectangular array of plasma spheres where the sides of the unit cell are denoted by a and b , respectively. θ is the angle between the incident wavevector $\mathbf{k}$ and the vector $\mathbf{n}$ which is normal to the plane of spheres (xy -plane). ϕ is the angle between the parallel (to the xy -plane) component of the wavevector and the x -axis.

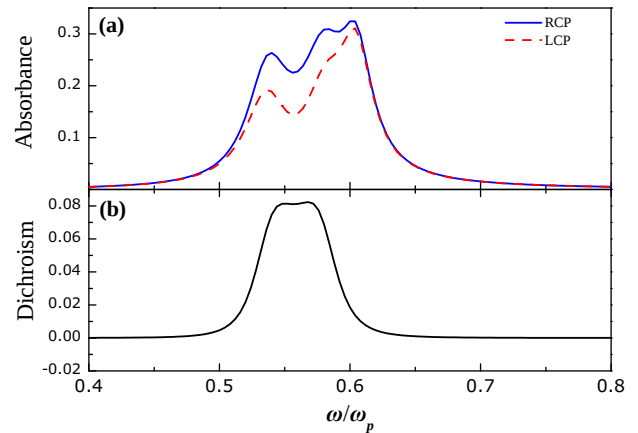


Fig. 2. (Color online) (a) Absorbance spectra for right- (solid line) and left-circularly (broken line) polarized light incident at angles $\theta = \phi = 45^\circ$ (see Fig. 1 for their definition) on a rectangular ($a = b/2 = c/\omega_p$) array of plasma spheres ($S = 0.3c/\omega_p$). (b) The corresponding circular dichroism spectrum of the above system of plasma spheres.

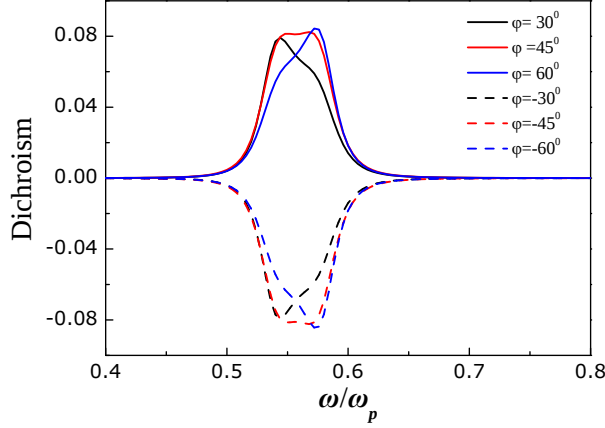


Fig. 3. (Color online) Circular dichroism spectra for $\theta = 45^\circ$ and for various values of the angle ϕ (shown in the inset) for the array of plasma spheres of Fig. 2.

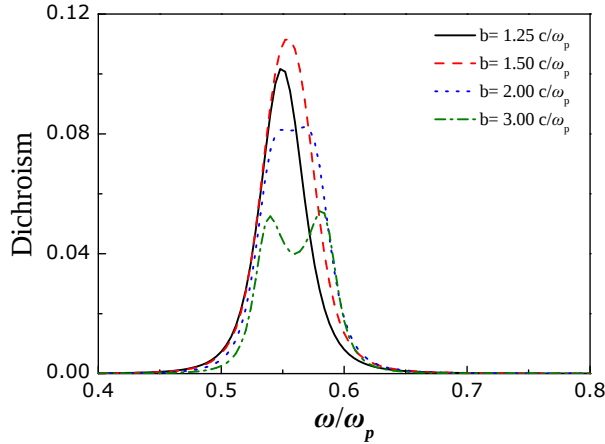


Fig. 4. (Color online) Circular dichroism spectra for $\theta = \phi = 45^\circ$ and different rectangular arrays of plasma spheres ($S = 0.3c/\omega_p$) with $a = c/\omega_p$ and b as shown in the inset.

References

1. J. B. Pendry, “Negative refraction make a perfect lens,” *Phys. Rev. Lett.* **85**, 3966 (2000).

2. R. A. Shelby, D. R. Smith and S. Schultz “Experimental Verification of a Negative Index of Refraction,” *Science* **292**, 77 (2001).
3. J. B. Pendry, “A Chiral Route to Negative Refraction,” *Science* **306**, 1353 (2004).
4. A. Lakhtakia, “Conjugation symmetry in linear electromagnetism in extension of materials with negative real permittivity and permeability scalars,” *Microwave Opt. Technol. Lett.* **33**, 96 (2002).
5. S. Tretyakov, I. Nefedov, A. Shivala, S. Maslovski, and C. Simovski, “Waves and energy in chiral nihility,” *J. Electromag. Waves Appl.* **17**, 695 (2003).
6. T. G. Mackay and A. Lakhtakia, “Plane waves with negative phase velocity in Faraday chiral mediums,” *Phys. Rev. E* **69**, 026602 (2004).
7. T. G. Mackay and A. Lakhtakia, “Negative phase velocity in a material with simultaneous mirror-conjugated and racemic chirality characteristics,” *New J. Phys.* **7**, 165 (2005).
8. C. Monzon and D. W. Forester, “Negative Refraction and Focusing of Circularly Polarized Waves in Optically Active Media,” *Phys. Rev. Lett.* **95**, 123904 (2005).
9. S. Tretyakov, A. Shivala, and L. Jylhä,

- “Backward-wave regime and negative refraction in chiral composites,” *Photon. Nanostruct.* **3**, 107 (2005).
10. J. Q. Shen, “Negative refractive index in gyrotropically magnetoelectric media,” *Phys. Rev. B* **73**, 045113 (2006).
 11. V. M. Agranovitch, Yu. N. Garstein and A. A. Zakhidov, “Negative refraction in gyrotropic media,” *Phys. Rev. B* **73**, 045114 (2006).
 12. V. Yannopapas, “Negative index of refraction in artificial chiral materials,” *J. Phys.: Condens. Matter* **18**, 6883 (2006).
 13. A. Baev, M. Samoc, P. N. Prasad, M. Krykunov, and J. Autschbach, “A quantum chemical approach to the design of chiral negative index materials,” *Opt. Express* **15**, 5730 (2007).
 14. D. -H. Kwon, D. H. Werner, A. V. Kildishev, and V. M. Shalaev, “Material parameter retrieval procedure for general bi-isotropic metamaterials and its application to optical chiral negative-index metamaterial design,” *Opt. Express* **16**, 11822 (2008).
 15. A. V. Rogacheva, V. A. Fedotov, A. S. Schwanecke, and N. I. Zheludev, “Giant gyrotropy due to electromagnetic-field coupling in a bilayered chiral structure,” *Phys. Rev. Lett.* **97**, 177401 (2006).
 16. E. Plum, J. Dong, J. Zhou, V. A. Fedotov, T. Koschny, C. M. Soukoulis, and N. I. Zheludev, “3D-Chiral Metamaterial Showing Artificial Magnetic Response and Negative Refraction,” arXiv: 0806.0823v1 (2008).
 17. E. Plum, V. A. Fedotov, and N. I. Zheludev, “Optical activity in extrinsically chiral metamaterial,” *Appl. Phys. Lett.* **93**, 191911 (2008).
 18. E. Plum, V. A. Fedotov, and N. I. Zheludev, “Optical Activity of Planar Achiral Metamaterials,” arxiv.org: 0807.0523v1 (2008).
 19. M. Decker, M. W. Klein, M. Wegener, and S. Linden, “Circular dichroism of planar chiral magnetic metamaterials,” *Opt. Lett.* **32**, 856 (2007).
 20. E. Plum, V. A. Fedotov, A. S. Schwanecke, N. I. Zheludev, and Y. Chen, “Giant optical gyrotropy due to electromagnetic coupling,” *Appl. Phys. Lett.* **90**, 223113 (2007).
 21. A. S. Schwanecke, V. A. Fedotov, V. V. Khardikov, S. L. Prosvirnin, Y. Chen, and N. I. Zheludev, “Nanostructured metal film with asymmetric optical transmission,” *Nano Lett.* **8**, 2940 (2008).
 22. N. Stefanou, V. Karathanos and A. Modinos, “Scattering of electromagnetic waves by periodic structures,”

- J. Phys.: Condens. Matter **4**, 7389 (1992).
23. N. Stefanou, V. Yannopapas, and A. Modinos, "Heterostructures of photonic crystals: frequency bands and transmission coefficients," Comput. Phys. Commun. **113**, 49 (1998); N. Stefanou, V. Yannopapas, and A. Modinos, "MULTEM 2: A new version of the program for transmission and band-structure calculations of photonic crystals," Comput. Phys. Commun. **132**, 189 (2000).
 24. V. Yannopapas and N. Stefanou, "Optical excitation of coupled waveguide-particle plasmon modes: A theoretical analysis," Phys. Rev. B **69**, 012408 (2004).
 25. C. W. Bunn, *Chemical Crystallography* (Oxford University Press, New York, 1945).
 26. A. Taleb, V. Russier, A. Courty, and M. P. Pileni, "Collective optical properties of silver nanoparticles organized in two-dimensional superlattices," Phys. Rev. B **59**, 13350 (1999).